

SENSORS, FOCUS ON TACTILE,  
FORCE AND STRESS SENSORS



**SENSORS, FOCUS ON TACTILE,  
FORCE AND STRESS SENSORS**

EDITED BY  
JOSE GERARDO ROCHA  
AND  
SENENTXU LANCEROS-MENDEZ

***I-Tech***

Published by In-Teh

In-Teh is Croatian branch of I-Tech Education and Publishing KG, Vienna, Austria.

Abstracting and non-profit use of the material is permitted with credit to the source. Statements and opinions expressed in the chapters are these of the individual contributors and not necessarily those of the editors or publisher. No responsibility is accepted for the accuracy of information contained in the published articles. Publisher assumes no responsibility liability for any damage or injury to persons or property arising out of the use of any materials, instructions, methods or ideas contained inside. After this work has been published by the In-Teh, authors have the right to republish it, in whole or part, in any publication of which they are an author or editor, and the make other personal use of the work.

© 2008 In-teh

[www.in-teh.org](http://www.in-teh.org)

Additional copies can be obtained from:

[publication@ars-journal.com](mailto:publication@ars-journal.com)

First published December 2008

Printed in Croatia

p. cm.

ISBN 978-953-7619-31-2

1. Sensors, Focus on Tactile, Force and Stress Sensors, Jose Gerardo Rocha and Senentxu Lanceros-Mendez

## Preface

This decade has been called by many people as the decade of the sensors. With an enormous increase in the research and application of sensors in the last fifteen years, it can be considered that a revolution similar to the one of microcomputers in the decade of 1980 is in course. In the last times, we have witnessed enormous advances in sensor's technology and more innovations are in the way. The sensitivity of the sensors is becoming higher, their dimensions lower, their selectivity better and their price lower. Some issues remain nevertheless constant: the basic principles used in the project of sensors and applications, once these principles are governed by the laws of the nature. However, through the times our appreciation, knowledge and mastering of these same laws has changed.

Among the existing sensors to measure the most diverse quantities, the tactile and force sensors are becoming more popular mainly, but not only, in the field of the robotic applications, where the machines are instructed to execute tasks more and more similar to the ones executed by human operators.

Tactile sensors are devices that measure the parameters related to the contact between the sensor itself and a certain object. This interaction is restricted to a well defined and usually small region. In contrast, the force and torque sensors normally measure the total forces and torques applied to an object.

Tactile sensors can be used to detect a wide range of stimulus: from the simple identification of a contact with a given object to a complete tactile image giving information on forces and shapes, for example. Usually, the active component of a tactile sensor is capable to feel and measure several properties, like contact forces, texture, impact, sliding and other contact conditions that can generate specific patterns of force and position. This information can be used to identify the state of the object handled by a manipulator, that is, its size, shape or if it is in the correct position, for example.

Once it does not exist a complete theory that describes the requirements of a robotic system in terms of tactile information, most of the knowledge in this area is produced from the study of the human tactile sensors and the way humans grasp and handle. From these studies, the investigators concluded that the function of grasping within the incorporation of tactile feelings requires several sensors, namely force sliding and even temperature knowledge. Moreover, the manipulator must have in its memory the right way to handle the object, that is, it must know a priori which are the sensations produced by the object, in order to handle it correctly.

This book describes some devices that are commonly identified as tactile or force sensors. It is achieved with different degrees of detail, in a unique and actual resource, the

description of different approaches to this type of sensors. Understanding the design and the working principles of the sensors described here, requires a multidisciplinary background of electrical engineering, mechanical engineering, physics, biology, etc. It has been made an attempt to place side by side the most pertinent information in order to reach a more productive reading not only to professionals dedicated to the design of tactile sensors, but also all other sensor users, as for example, in the field of robotics. The latest technologies presented in this book, are more focused on information readout and processing: as new materials, micro and sub-micro sensors are available, wireless transmission and processing of the sensorial information, as well as some innovative methodologies for obtaining and interpreting tactile information are also strongly evolving.

This book is organized in twenty four chapters. In the first chapters, some considerations concerning tactile sensors and the way they must operate, as well as some examples of silicon sensors are presented. Then, tactile sensors of three and six axes are described. Some of them can measure, beyond the force, the slip. After that, several flexible sensors with anthropomorphous characteristics and with particularities resembling the human skin are reported. Finally, some methods of transmission and information processing, namely wireless and with more or less elaborated algorithms are described.

December, 2008

Editors

**Jose Gerardo Rocha**  
**and**  
**Senentxu Lanceros-Mendez**  
*University of Minho,*  
*Portugal*

## Contents

Preface	V
1. How tactile sensors should be? <i>Satoshi Saga</i>	001
2. Torque Sensors for Robot Joint Control <i>Dzmitry Tsetserukou and Susumu Tachi</i>	015
3. CMOS Force Sensor with Scanning Signal Process Circuit for Vertical Probe Card <i>Jung-Tang Huang, Kuo-Yu Lee and Ming-Chieh Chiu</i>	037
4. Three-Dimensional Silicon Smart Tactile Imager Using Large Deformation of Swollen Diaphragm with Integrated Piezoresistor Pixel Circuits <i>Hidekuni Takao and Makoto Ishida</i>	053
5. High-Sensitivity and High-Stiffness Force Sensor Using Strain-Deformation Expansion Mechanism <i>Yong Yu Takashi Chaen and Showzow Tsujio</i>	073
6. High-Precision Three-Axis Force Sensor for Five-Fingered Haptic Interface <i>Takahiro Endo, Haruhisa Kawasaki, Kazumi Kouketsu and Tetsuya Mouri</i>	087
7. Optical Three-axis Tactile Sensor for Robotic Fingers <i>Masahiro Ohka, Jumpei Takata, Hiroaki Kobayashi, Hirofumi Suzuki, Nobuyuki Morisawa and Hanafiah Bin Yussof</i>	103
8. Measurement Principles of Optical Three-Axis Tactile Sensor and its Application to Robotic Fingers System <i>Hanafiah Yussof, Jumpei Takata and Masahiro Ohka</i>	123

---

9. Three Dimensional Capacitive Force Sensor for Tactile Applications	143
<i>Jose Gerardo Rocha and Senentxu Lancers-Mendez</i>	
10. Study on Dynamic Characteristics of Six-axis Wrist Force/torque Sensor	163
<i>Ke-Jun Xu</i>	
11. Performance Analysis and Optimization of Sizable 6-axis Force Sensor Based on Stewart Platform	205
<i>Y. Z. Zhao, T. S. Zhao, L. H. Liu, H. Bian and N. Li</i>	
12. Grip Force and Slip Analysis in Robotic Grasp: New Stochastic Paradigm Through Sensor Data Fusion	217
<i>Debanik Roy</i>	
13. Development of Anthropomorphic Robot Hand with Tactile Sensor: SKKU Hand II	253
<i>Byung June Choi, Jooyoung Chun and Hyouk Ryeol Choi</i>	
14. Design of a Tactile Sensor for Robot Hands	271
<i>Giorgio Cannata and Marco Maggiali</i>	
15. Tactile Sensing for Robotic Applications	289
<i>Ravinder S. Dahiya and Maurizio Valle</i>	
16. Fast and Accurate Tactile Sensor System for a Human-Interactive Robot	305
<i>Toshiharu Mukai, Shinya Hirano and Yo Kato</i>	
17. Development of a Humanoid with Distributed Multi-axis Deformation Sense with Full-Body Soft Plastic Foam Cover as Flesh of a Robot	319
<i>Marika Hayashi, Tomoaki Yoshikai and Masayuki Inaba</i>	
18. Research and Preparation Method of Flexible Tactile Sensor Material	325
<i>Ying Huang, Min Wang, Huaili Qiu, Bei Xiang and Yugang Zhang</i>	
19. A Principle and Characteristics of a Flexible and Stretchable Tactile Sensor Based on Static Electricity	341
<i>Yasunori Tada, Masahiro Inoue, Toshimi Kawasaki, Yasushi Kawahito, Hiroshi Ishiguro and Katsuaki Suganuma</i>	
20. Design Considerations for Multimodal “Sensitive Skins” for Robotic Companions	353
<i>Walter Dan Stiehl</i>	

- 
- |  |     |
|--|-----|
| 21. Compliant Tactile Sensors for High-Aspect-Ratio Form Metrology<br><i>Erwin Peiner</i>  | 377 |
| 22. Tactile Sensor Without Wire and Sensing Element in the Tactile Region<br>using New Rubber Material<br><i>Yo Kato and Toshiharu Mukai</i> | 399 |
| 23. Recognition of Contact State of Four Layers Arrayed Type Tactile<br>Sensor by Using Neural Networks<br><i>Seiji Aoyagi</i>               | 409 |
| 24. Tactile Information Processing for the Orientation Behaviour<br>of Sand Scorpions<br><i>DaeEun Kim</i>                                   | 431 |



# Tactile Sensor Without Wire and Sensing Element in the Tactile Region using New Rubber Material

Yo Kato and Toshiharu Mukai  
*Bio-Mimetic Control Research Center, RIKEN  
Japan*

## 1. Introduction

Recently the idea of covering a robot's surface with a 'skin' of soft tactile sensors has attracted the attention of researchers, and some human-interactive robots covered with such sensors have actually been made (Tajima et al., 2002; Kanda et al., 2002). However, most conventional tactile sensors need a large number of sensing elements and wires because every detection point needs one sensing element and wiring to an A/D converter. There are some studies aiming to overcome this wiring problem by using 2D surface communication or wireless communication (Shinoda & Oasa, 2000; Ohmura et al., 2006), but these are very complicated and expensive solutions.

We have developed a soft areal tactile sensor made of pressure-sensitive conductive rubber without any wire or sensing element in the tactile region. The distribution of applied pressure, relating to the resistivity change of the pressure-sensitive rubber, can be estimated by using inverse problem theory. We employed electrical impedance tomography (EIT) to reconstruct the resistivity distribution from information obtained by electrodes placed around the region.

EIT is an established method in medical and industrial applications (Holder, 2005), but it has not been applied to tactile sensors until recently. Nagakubo and Alirezaei proposed a tactile sensor using an EIT algorithm operating with commonly used EIT software and commercially available pressure-sensitive rubber (Nagakubo & Kuniyoshi, 2006; Alirezaei et al., 2006). Their method is based on the same principle as ours, but their pressure-sensitive conductive rubber is not suitable for this method. We have newly developed special pressure-sensitive conductive rubber for this sensor, and adopted a new computation technique suitable for this rubber. We have also developed a prototype sensor system that can measure pressure distribution in real-time.

In this paper, we describe basic structure and computation technique of our sensor system, as well as experimental results obtained using our prototype sensor system.

## 2. Device design

### 2.1 Basic structure

We have developed, in collaboration with Tokai rubber industries, Ltd., a new type of pressure-sensitive conductive rubber, the resistivity of which increases when pressure is

applied, unlike ordinary conductive rubber. This new rubber is suitable for a tactile sensor using EIT, because its initial resistivity can be set low, which leads to the accurate reconstruction of pressure distribution from voltage measurements with relatively low noise. Fig. 1 shows the dimensions of the pressure-sensitive conductive rubber that we used in experiments. We formed the rubber into a 1-mm-thick, 195-mm-diameter disc and put 16 electrodes around the disc by vulcanization gluing at regular intervals.

This rubber also has the important feature that its resistivity increases in either case where compressive or tensile strain is applied to it. Fig. 2 shows the relationship between the distortion factor and the resistivity of the rubber. The filled circles are for the compressive case, and the open triangles are for the tensile case. We confirmed that the resistivity increases regardless of the type of strain (i.e. any type of stress).

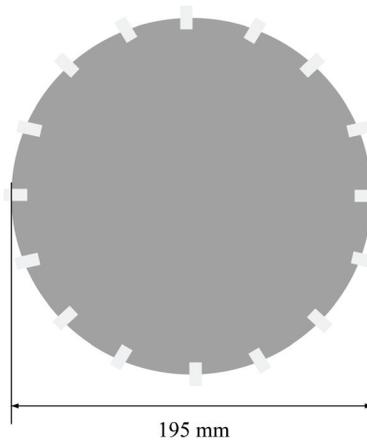


Fig. 1. Pressure-sensitive conductive rubber sheet with 16 electrodes

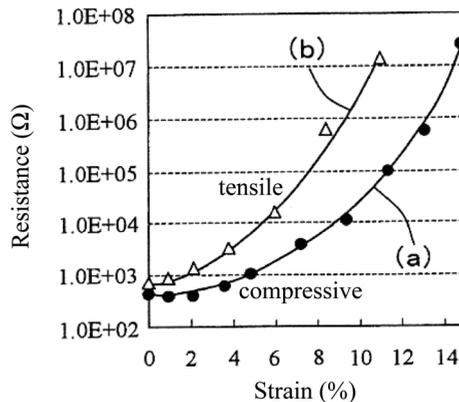


Fig. 2. Resistance changes depends on a) compressive, and b) tensile strains

## 2.2 Measurement system

The processing of our tactile sensor consists of two steps. The first step is the measurement of conductivities using the 16 electrodes placed around the rubber sheet at even intervals.

An AC voltage is applied, and resistance is calculated using the four-electrode method from the differential voltage between neighboring electrodes, for every possible combination (Fig. 3). In the figure, alternating voltage is supplied between the first and second electrodes and the differential voltage is measured between the 10th and 11th electrodes. The number of possible combinations is 208. However, the number of the independent measured data is actually 104, because the measurements when the supply and the measuring electrode pairs are symmetrically positioned are not independent.

This basic measurement procedure of EIT was developed at Sheffield University (In the original method, current source is used, but we use voltage source instead, for circuit simplicity). The main advantages of this procedure are that it is relatively precise and easy. We can measure at quite a high rate by switching measurement electrodes with a higher frequency AC voltage. In the experiment, we used a 3.685kHz, 4.5 V<sub>pp</sub> AC voltage. This frequency was determined from the conversion speed of an A/D converter in our sensor controller, dsPIC board, described below.

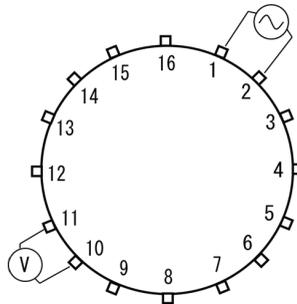


Fig. 3. Conductivity measurement method

### 2.3 Reconstruction algorithm

In the second step, the distribution of resistivity change is reconstructed from the measurements. This distribution also indicates the pressure distribution because the resistivity change is caused by the change of the pressure applied to the sheet. To get a reconstruction image, we use a sensitivity matrix (Kotre, 1989) that is the Jacobian matrix between  $\delta V$  and  $\delta \rho$ .

$$\delta V(m,n) = S_{m,n,x,y} \delta \rho(x,y) \quad (1)$$

Here,  $m$  and  $n$  indicate the position of the applying electrode pair and the measuring electrode pair, respectively, and  $x$  and  $y$  indicate the position coordinates of the discrete domain in the rubber plate.

The sensitivity matrix can be obtained by numerically solving a forward problem. Then solving (1) by using a least squares (Lawson & Hanson, 1974) or generalized inverse matrix method, the distribution of resistivity change  $\delta \rho(x,y)$  is obtained. However this is inverse problem. The inverse solution is apt to become instable and, in our case, the ordinary least squares method does not work because of this instability. To overcome this problem, inverse problem theory suggests various normalization methods. We employed the positive value constraint, because we can assume that the resistivity change is always positive thanks to our new pressure-sensitive conductive rubber, unlike ordinary EIT method that uses the regularization technique.

Equation (2) shows the least squares method with a non-negative constraint. In the next section, we show that the constraint successfully stabilizes the solution. In the case of EIT,  $A$ ,  $x$ ,  $b$  are corresponding to  $S$ ,  $\delta\rho$ ,  $\delta V$ .

$$\min_x \|Ax - b\|^2 \quad (x \geq 0) \quad (2)$$

This method needs the sensitivity matrix in advance; we calculate the matrix using (3).

$$S_{m,n,x,y} = \int_a \nabla\phi_m \cdot \nabla\phi_n da \quad (3)$$

Here,  $\nabla\phi_m$  and  $\nabla\phi_n$  are the electric potential gradient, which is derived from the electric supply from the electrode pair of  $m$  or  $n$ , respectively. In other words, we can calculate each component of the sensitivity matrix by integrating the inner products of the potential gradients that are caused by the electric current from  $m$  and  $n$  electrode pairs in the area indicated by  $x$  and  $y$ . This equation can be derived from electromagnetic theory.

Fig. 4 shows the example calculation results of the inner products. These solutions are obtained by using the Partial Differential Equation Toolbox on MATLAB (The MathWorks Inc.).

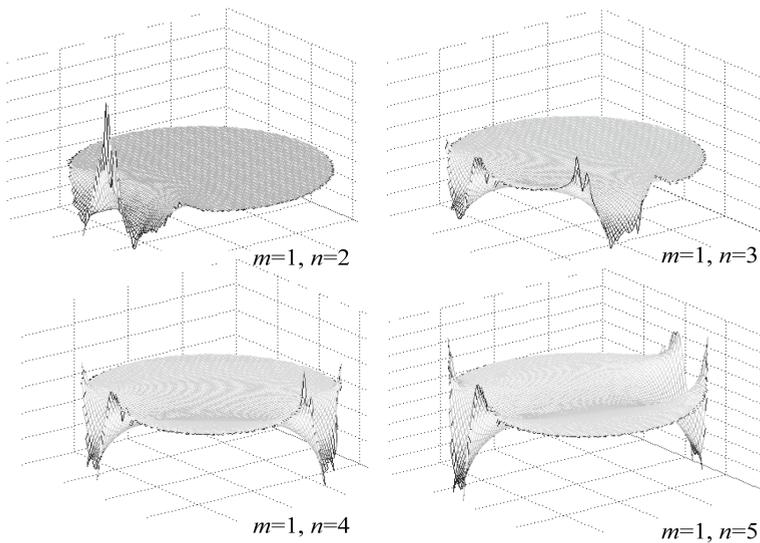


Fig. 4. Example calculation results of the inner product of the potential gradients that caused by  $m$  and  $n$  electrode pairs

### 3. Reconstruction experiments

We conducted experiments to determine the performance of our tactile sensor. The measurement conditions were as follows (Kato et al., 2008).

We measured the potential of all electrodes by using sensor controller and driver board (Fig. 5). The main controller is dsPIC board that is a general-purpose 35x50 mm<sup>2</sup>

sensing/controlling board we developed, having a dsPIC (Microchip technology 30F6012A) as the CPU and a USB interface IC (FTDI FT232RL) for 1 Mbps communication. It has many connectors through which most pins are accessed. It also has a stacking connector for an extension board. A tactile sensor controller we developed based on the dsPIC board uses a 12 bit A/D converter and digital I/Os in the 30F6012A. Its program is written in C and downloaded in flash memory of the 30F6012A, as firmware. Within dsPIC board, all measurement is done using Lock-in amp method. Lock-in amp method is very durable to noise and can be effectively treated by DSP module in dsPIC. The collected data are sending to PC via USB. The reconstruction algorithm is treated by PC.



Fig. 5. Sensor controller and driver consisting of dsPIC board and extension board

The reconstruction algorithm produced the intensity distribution image of the change in resistivity from 208 measured values (Redundant pairs were measured for noise tolerance). The relation between the change in resistivity and pressure distribution is not perfectly clear, but we can conjecture it from Fig. 2. To display the reconstruction image in gray scale, we smoothed the image by inserting interpolation pixels among the pixels that represented actual data. We found that this interpolation successfully displayed a natural distribution image through the anti-aliasing effect when the pressure point was spread over more than one reconstruction domain.

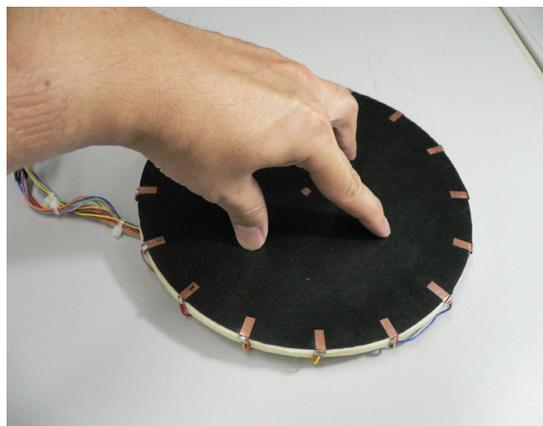


Fig. 6. Point pressures are applying by fingers

First, we tested the stabilization ability of our non-negative least squares algorithm. We applied point pressures by finger as shown in Fig. 6. We compared the reconstruction images generated using a generalized inverse matrix method and those generated using the non-negative least squares method from the same data. The non-negative constraint successfully stabilized the solution, as shown in Fig. 7, while the generalized inverse matrix method failed. The image obtained by non-negative least squares was very stable, and we found that areal tactile sensor functioned well enough for practical usage.

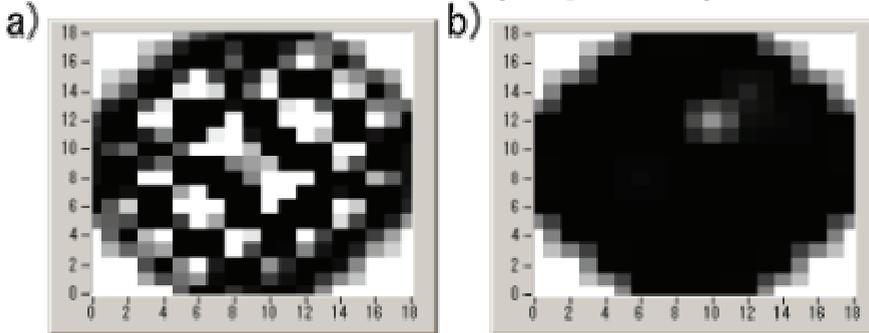


Fig. 7. Comparison between ordinal least square solution and non-negative least square solution from the same input data a) ordinal least square solution, b) non-negative least square solution

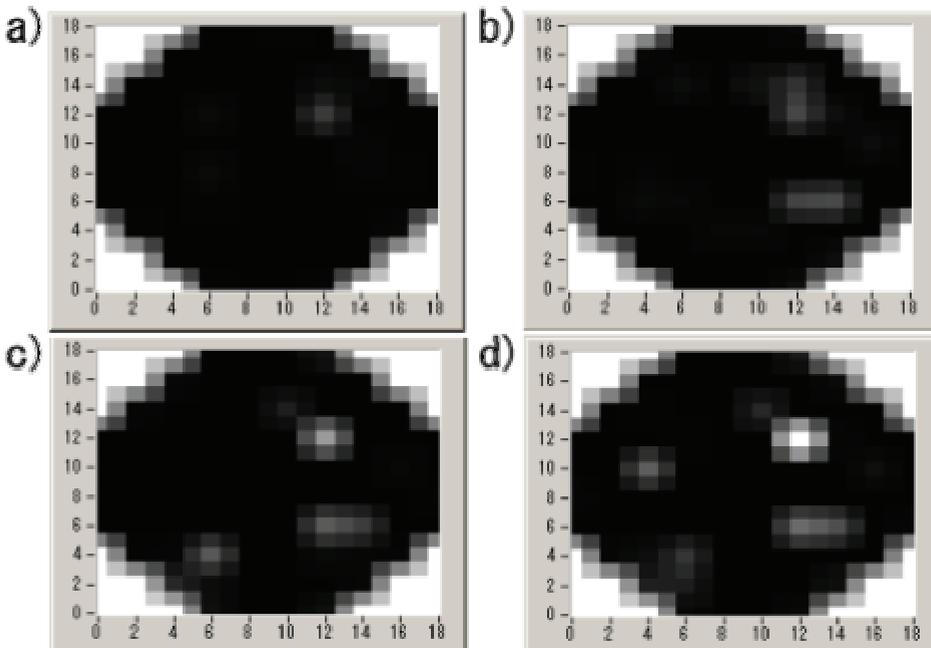


Fig. 8. Reconstructed pressure distribution when three or four point pressures are applied at a time a) a pressure point, b) two pressure points, c) three pressure points and d) four pressure points

Next, we tested multiple pressure points. Fig. 8 shows reconstructed images when applying multiple pressure points by fingers. The images, from the upper left to the lower right, show the reconstruction results when pressure applied to one, two, three or four points. We found that the non-negative least squares algorithm makes it possible to recognize individual pressure points.

Lastly, we measured the update time including the measurement time and reconstruction time. The update time was about 360ms. This is relatively slow; however, we can improve the time by optimizing measurement process.

#### 4. Confirmation of basic performance

To examine basic tactile sensor performance, we compared experiments using a digital force gauge (Shimpo FGC-2B) as shown in Fig. 9 under the same conditions as in previous sections. A disk-like tip of 25mm in diameter was attached to the digital force gauge to apply force to conductive rubber. Data was collected in parallel by tactile sensors.

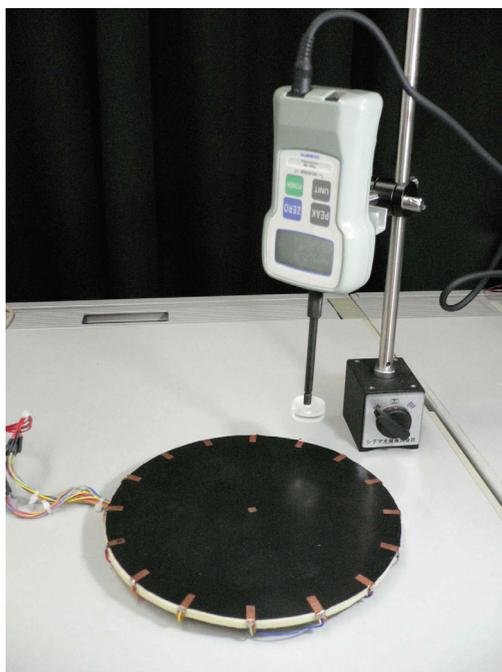


Fig. 9. Experimental setup using digital force gauge

Fig. 10 shows time-averaged reconstructed values by adding time-changing pressures by the force gauge at one point near the center. Since the tip of the force gauge is almost same size as the integration area -- 20mm in diameter -- corresponding to an element of the sensitivity matrix, responses were expected to appear on only one or a few adjacent elements, which was confirmed by results. When the location for adding force was changed, the area expressing the peak also changed. When peaks appeared in multiple areas, they were in areas adjacent to each other.



To estimate noise, we measured signal to noise ratio, assuming 2-norm of the voltage measurement vector in the unloaded condition as noise and 2-norm of the voltage vector approximated by the least squares method with a force of 25N applied to one point as a signal. The ratio was found to be 27dB.

## 5. Conclusion

We developed a tactile sensor system based on the EIT method that has no wire or sensing elements in the tactile region. We believe that the sensor system is extremely durable to shocks and large transformations, and is low cost because there is no wire or sensing elements. We obtained good results from the experiments investigating the basic performance of our sensor system. The ordinary EIT algorithm assumes not only positive reconstructed values but also negative values, which leads to instability in reconstruction with noisy data. We restrict the reconstructed values to positive, which is justified by using a new kind of rubber whose electrical resistivity always increases in response to applied deformation.

In the future, we will improve the accuracy of the sensor and shorten the measurement time. We will also mount sensors as artificial sensitive skin on various objects (e.g. robots, seats and bumpers of automobile).

## 6. References

- Alirezaei, H.; Nagakubo, A. & Kuniyoshi, Y. (2006). A tactile sensor based on inverse problem theory: Basic experiments, in *Proc. the 24th Annual Conference of the Robotics Society of Japan*, 1C32 (in Japanese)
- Holder, S. D. (2005). *Electrical Impedance Tomography: Methods, History and Applications*, Inst. of Physics Pub. Inc.
- Kanda, T.; Ishiguro, H.; Ono, T.; Imai, M. & Nakatsu, R. (2002). Development and evaluation of an interactive humanoid robot 'Robovie', in *Proc. ICRA2002*, pp. 4166-4173
- Kato, Y.; Hayakawa, T. & Mukai, T. (2008). Soft areal tactile sensor using tomography algorithm, *Journal of Robotics and Mechatronics*, Vol. 20, No. 4 (In press)
- Kotre, C. J. (1989). A sensitivity coefficient method for the reconstruction of electrical impedance tomograms, *Clinical physics and physiological measurement*, Vol. 10, pp. 275-281
- Lawson, C. L. & Hanson, R. J. (1974). *Solving Least-Squares Problems*, Prentice-Hall, Chapter 23
- Nagakubo, A. & Kuniyoshi, Y. (2006). A tactile sensor based on inverse problem theory: The principle, in *Proc. the 24th Annual Conference of the Robotics Society of Japan*, 1C31 (in Japanese)
- Ohmura, Y.; Kuniyoshi, Y. & Nagakubo, A. (2006). Conformable and scalable tactile sensor skin for curved surfaces, in *Proc. ICRA2006*, , pp. 1348-1353
- Shinoda, H. & Oasa, H. (2000). Wireless tactile sensing element using stress-sensitive resonator, *IEEE/ASME Trans. on Mechatronics*, Vol. 5, No. 3, pp.258-265

Tajima, R.; Kagami, S.; Inaba, M. & Inoue, H. (2002). Development of soft and distributed tactile sensors and the application to a humanoid robot, *Advanced Robotics*, Vol. 16, No. 4, pp.381-397